

Dielectric behavior and Ac conductivity measurements of bulk (TiO₂, ZnO/Epoxy) composites.

دراسة السلوك العازل الكهربائي والتوصيلية الكهربائية المتناوبة لتمراكبات (راتنج الايبوكسي - اوكسيد التيتانيوم) و(راتنج الايبوكسي - اوكسيد الزنك)

Abdullah A. Hussein¹, Abdulwahab. A.Sultan², Tahseen A. Saki³

¹Department of Material Science, Polymer Research Centre, University of Basra

² Petrochemical department, Basra Technical College

³ Chemistry department, College Science, Basra University of Basra.

ABSTRACT:

Dielectric behavior and ac conductivity measurements on epoxy resin filled with (5, 10, 15, 20, 25 wt.%) micro sized particles of TiO₂ and ZnO have been studied.. The measurements were carried out in the frequency range (120Hz - 2MHz) and over a wide temperature 30 °C and 110°C. Different dielectric behavior was observed depending on filler type, filler contact, frequency and temperature.

Results show that dielectric permittivity (ϵ') and dielectric loss(ϵ'') increases with the addition of epoxy resin, which has been attributed to interfacial polarization. The value of (ϵ') increased with increasing temperature, due to the greater freedom for movement of the dipole molecular chains within the epoxy at high temperature. The value of (ϵ') decreases with increasing frequency, which indicates that the major contribution to the polarization comes from orientation polarization. Interfacial relaxation is found to be strongly dependent on the presence of micro-filler particles. The Alternating Current (AC) conductivity increases as the temperature and frequency, because of the segmental mobility and electrical conduction.

Key word: dielectric spectroscopy, ac conductivity, epoxy resin, TiO₂, ZnO.

الخلاصة

تمت دراسة السلوك العازل الكهربائي والتوصيلية الكهربائية المتناوبة لراتنج الايبوكسي المضاد إليه حشوات اوكسيد التيتانيوم و اوكسيد الزنك بنسب وزنيه (5, 10, 15, 20, 25 wt.%). أجريت القياسات العملية لسلوك العزل الكهربائي عند مدى الترددات (120Hz - 2MHz) ودرجة حرارة °C (30 – 110). ان اختلاف السلوك العازل للمترابكات المحضرة يعتمد على نوع ومحتوى الحشوة والتردد ودرجة الحرارة. أظهرت النتائج المختبرية بان سماحية العزل و فقد العازل تزداد بزيادة محتوى الحشوة والذي قد تعزى إلى ظهور الاستقطاب البيئي، كذلك تزداد السماحية بزيادة درجة الحرارة نتيجة لزيادة حرية الحركة للسلاسل الجزيئية لثنائيات الأقطاب داخل الايبوكسي عند درجة حرارة عالية، وتقل السماحية بزيادة التردد بسبب الاستقطاب ألتجاهي. كذلك تم الاستنتاج على إن الاسترخاء البيئي يعتمد على الحجم ألدقائق للحشوة. التوصيلية الكهربائية المتناوبة تزداد بزيادة درجة الحرارة والتردد بسبب حركة الشحنات الحرة و تيار التوصيل.

INTRODUCTION:-

In the last decade many research teams from all over the world have focused their energies toward studies on polymer composites as effective materials for electrical insulation [1].The increasing interest in the behavior of these newly born dielectrics is mainly due to the fact that these materials possess a huge filler – polymer matrix interface which has a major influence on the electrical, thermal and mechanical properties [2].

Epoxy and epoxy based composites are preferred insulating materials for several electrical applications, especially printed circuit boards, bushings, GIS spacers, motors, generator ground wall insulation system and cast resin transformers. This is because epoxy resins are excellent electrical insulators and protect electrical components from moisture, dust and short circuiting. Recently,

epoxy based dielectric systems are being increasingly investigated for their electrical properties, since the introduction of fillers demonstrate several advantages in their properties when compared with the similar properties obtained for epoxy systems with micrometer sized fillers [3,4]. For some interesting applications we need to improve the electrical conductivity of such adhesives. So the dispersion within the epoxy matrix of conductive powder particles with sufficient quantity allows reaching high electrical conductivity values and consequently conductive or semi-conductive composite is then formed. These composite polymeric materials have found a variety of applications because they constitute excellent models for studying the interactions between condensed matter and electromagnetic radiation such as microwaves. They are also used for spatial applications [5].

Titanium dioxide and zinc oxide are extensively studied because of their interesting chemical, electrical and optical properties used as semiconductor, catalytic, dielectric materials, high-density dynamic-memory devices, capacitors in microelectronics, insulator gate in MIS structures, etc [6, 7].

Polymers such as polyethylene, polypropylene, epoxy resins and silicone rubbers are combined with fillers such as layered silicate (LS), silica (SiO₂), Titanium dioxide (TiO₂), zinc oxide (ZnO) and alumina (Al₂O₃) [8]. The properties of composites certainly depend on the kind of particle materials, physical and chemical conditions of their surfaces, the kind of coupling agents to bridge inorganic and organic substances chemically and physically, the kind and content of compatibilizers and/or dispersants, and the kind of polymer matrices. [9-11].

EXPERIMENTAL:

Materials:

The materials tested in this study were (epoxy resin- TiO₂) and (epoxy resin- ZnO) composites, as well as epoxy polymer. The polymer matrix was a Bisphenol-A based epoxy resin of type diglycidylether of bisphenol-A (DGEBA-368WG) Mw = 624 gm / mole, density =1.27 gm /cm³, and a Triethylenetetramine (TETA) , supplied by United Chemical Company Ltd. (UNICHEM, JORDEN) was used as hardener. The content of fillers of the tested formulations was (5, 10, 15, 20 and 25 wt.%). As for the fillers, highly pure grades of commercially available uncoated particles [filler size ≈ 0.25 μm for TiO₂ and ZnO] are procured from Sigma Aldrich .

Sample preparation :

The (TiO₂, ZnO) powders were added to the epoxy resin (as received) at weight contact and then mixed at about 70⁰C for 5 minutes, then curing agent triethylene tetra amine (TETA), TETA was added as hardener in the percent epoxy (1:4) and mixed for 5 minutes also. The mixture, then cast on clean aluminum substrates.

The initial curing was carried at room temperature for 24 hours, followed by post curing at 120⁰C for 2 hours, Circular aluminum electrodes in diameter (6mm) were vacuum deposited on the upper side of the composite sample, and thermosetting sheets of epoxy composites were made.

Characterization and measurements :

Dielectric properties of (TiO₂, ZnO /Epoxy) composites were investigated using Digital RCL bridge type (MEGGER B131), on a frequency range of 120 Hz and 1kHz. At the frequencies in the range (120Hz -2MHz) RCL bridge type (METRAPOINT-RLC2 and ME 1634 FUNCTION GENERATOR) were used to measure the capacitance of the samples. The impedance Z at different frequency up to 500 kHz was measured by RCL bridge type (Hewlett-Packard A 4800).

The real and imaginary parts of the complex dielectric permittivity ($\epsilon^* = \epsilon' - j \epsilon''$) were obtained with the assumption that studied cell is equivalent to a circuit consisting of an ideal capacitance Cp in parallel with a pure (ohmic) resistance Rp. The capacitance of a parallel-plate capacitor is, for the real case, when the losses are present [12]:

$$C = \epsilon^* C_0 = \epsilon_0 (\epsilon' - j \epsilon'') A / d \quad \dots\dots\dots (1)$$

where ϵ_0 is the absolute permittivity of the vacuum (8.854×10^{-12} F/m), ϵ' is the dielectric permittivity (the real part of the complex dielectric constant), ϵ'' is the imaginary part of the complex

permittivity, d is the distance between the plates, A is the area of a plate and C_0 is the capacitance of the empty cell

$$C_0 = \epsilon_0 A / d.$$

The dielectric permittivity is given by [13, 14]:

$$\epsilon' = C_p / C_0 \dots\dots\dots (2)$$

The imaginary part of the complex permittivity can be expressed as:

$$\epsilon'' = 1 / (C_0 R_p 2\pi f) \dots\dots\dots (3)$$

The dielectric loss for the real capacitor is given by:

$$\tan \delta = G / (2 \pi f C_p) = 1 / (2 \pi f C_p R_p) \dots\dots\dots (4)$$

where G is the electrical conductance, C_p capacity of parallel, resistance of parallel and f is the signal frequency.

By measuring C_p and R_p , eqs. (2), (3) and (4) permit to determine the values of ϵ' , ϵ'' and $\tan \delta$.

The a.c conductivity σ_{ac} for an ionic electrolyte material of all samples has been calculated from the dielectric losses according to the relation

$$\sigma_{ac} = \epsilon_0 \epsilon'' 2 \pi f \dots\dots\dots (5)$$

Result and Discussion:

The determination of the dielectric relaxations and a.c conductivity behavior of (TiO₂,ZnO-epoxy) composites is necessary to find its appropriate application[15]. The (TiO₂, ZnO) powder was mixed with epoxy to form composite with (5, 10, 15, 20and 25) wt.% filler. The dielectric permittivity (ϵ') of (TiO₂,ZnO-epoxy) composites as a function of filler content in two fixed frequencies 120Hz and 1kHz at room temperature is shown in figure1 (a&b). The addition of filler to the polymer increases the dielectric permittivity of the prepared composite as the filler content increases. That could be caused by relaxation process between the filler particles and the polymer matrix [16, 17].

Figure 2 (a&b) shows curves the variation of dielectric permittivity behavior for (TiO₂ /Epoxy) and (ZnO /Epoxy) composites as a function temperature in the range (30 – 110) °C at constant electric field frequency of 1kHz. It can be seen that, the values of (ϵ') of the composites lay between the values for the polymer and the values for the ceramics as expected. The value of (ϵ') increases with temperature at fixed frequency, this is true for all the samples at all frequencies. At lower frequencies this effect is more prominent. The increase in (ϵ') with temperature is due to greater freedom of movement of dipole molecular chain of polymer at high temperature. At lower temperature, as the dipoles are rigidly fixed in the dielectric, the field can not change the condition of dipoles. As the temperature increases, the dipoles comparatively become free and they respond to the applied electric field, thus polarization increases and hence dielectric constant is also increases with the increasing of temperature [18].

The variations of effective dielectric permittivity (ϵ') with respect to frequency for the epoxy composites with TiO₂ and ZnO fillers and at different filler contents are shown in Figure 3 (a&b) respectively. It is obvious that the dielectric permittivity decreases with the frequency for all of the TiO₂ and ZnO fillers concentration. The measurement temperature is maintained constant in this study; hence, its influence on the permittivity behavior can be neglected. The effective permittivity of composites is determined by dielectric polarization and relaxation mechanisms in the bulk of the composite material. Permittivity is a frequency dependent parameter in polymer systems. The epoxy component of permittivity is governed by the number of orient able dipoles present in the system and their ability to orient under an applied electric field [19,20]. Usually, the molecular groups which are attached perpendicular to the longitudinal polymer chain contribute to the dielectric relaxation mechanisms. At lower frequencies of applied voltage, all the free dipolar functional groups in the epoxy chain can orient themselves resulting in a higher permittivity value at these frequencies. As the electric field frequency increases, the bigger dipolar groups find it difficult to orient at the same pace as the alternating field, so the contributions of these dipolar groups to the

Table (1): The relaxation time of (TiO₂ ,ZnO /Epoxy) composites.

wt.%	TiO ₂ (Sec.) $\tau \times 10^{-4}$	ZnO (Sec.) $\tau \times 10^{-4}$
0	6.98	6.98
5	7.85	7.85
10	8.97	8.97
15	10.47	12.56
20	15.7	12.56
25	20.93	15.7

The effect of adding TiO₂ and ZnO fillers to the epoxy resin on ac conductivity as a function of temperature are shown in figure 8(a&b). It was noticed that the ac conductivity increases with the increasing of filler content for the same temperature circumstances. The observed increase in ac conductivity with temperature is due to the mobility of the charge carriers which is responsible for hopping. As the temperature increases the mobility of hopping ions also increases thereby increasing the conductivity. The electrons which are involved in hopping are responsible for electronic polarization in these composites [29].

AC conductivity as a function of frequency for TiO₂ and ZnO filled epoxy composites and unfilled epoxy is presented in figure 9(a&b). It was obvious that the ac conductivity increases for all cases in which filler were added. This increase in ac conductivity may relate to the interfacial polarization and electrical conduction [30].

Conclusions:

Frequency and temperature dependence of dielectric permittivity and dielectric loss in (TiO₂, ZnO /Epoxy) composites are studied in the frequency range (120Hz - 2MHz) and in the temperature range (30 -110 °C). Dielectric relaxations of an epoxy resin matrix and epoxy composites made by dispersing conductive micro particles (TiO₂ and ZnO) in the epoxy matrix were investigated. Interfacial or Maxwell-Wagner-Sillars effect (MWS) is evident in the dielectric spectrum of the pure epoxy resin matrix. Compared to (TiO₂, ZnO /Epoxy) composite, the permittivity of (TiO₂ /Epoxy) composite is higher than (ZnO /Epoxy) composite for all filler content due to electrical conductivity of TiO₂ filler particle

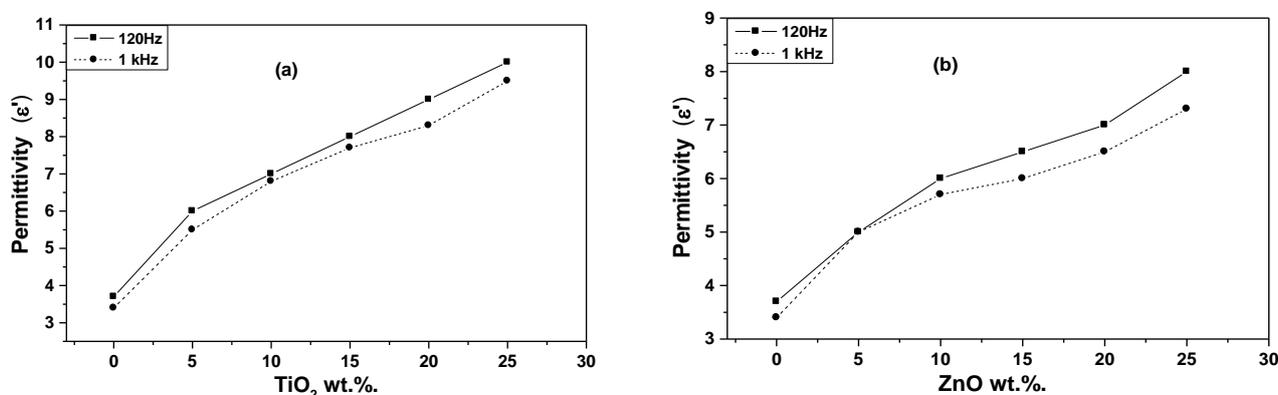


Fig. (1).Variation of permittivity with two different frequencies (a) TiO₂ and (b) ZnO

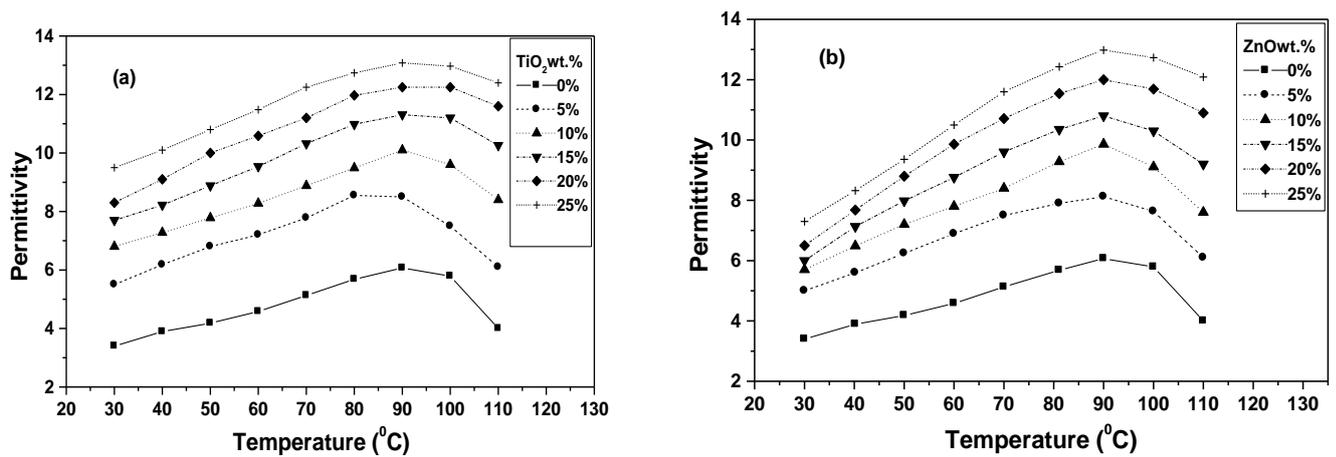


Fig. (2) Permittivity as a function of temperature for different content of (a) TiO₂ and (b) ZnO- epoxy composite.

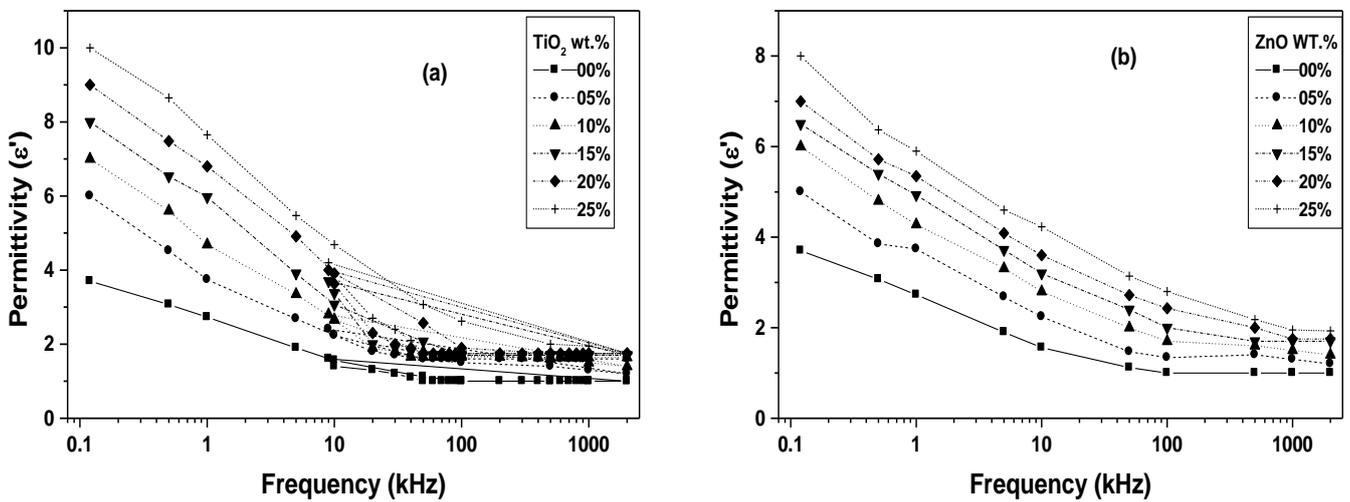


Fig. (3) The permittivity as a function frequency for different content of (a) TiO₂ and (b) ZnO- epoxy composite.

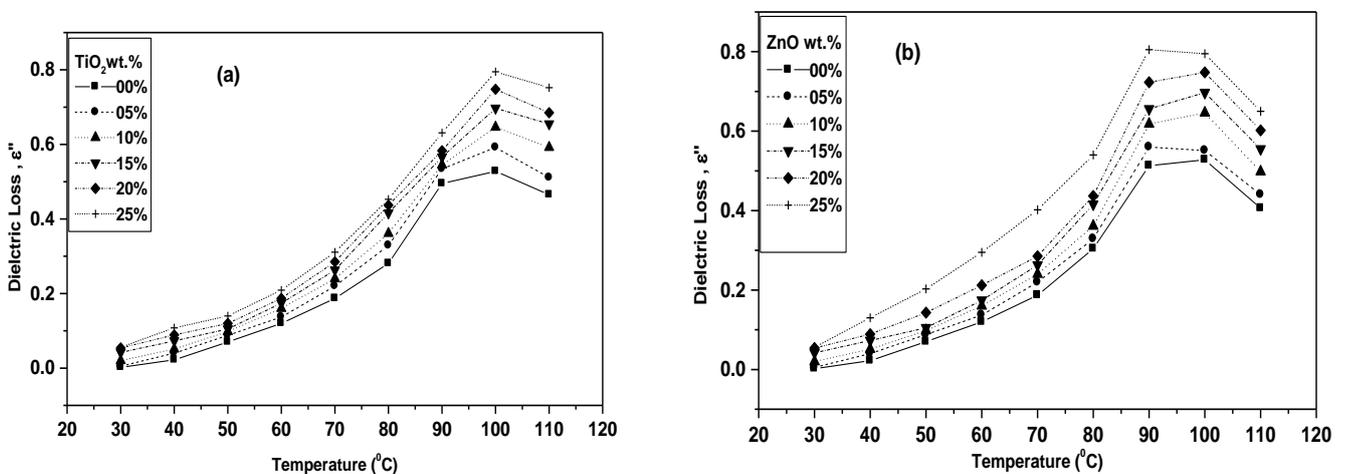


Fig. (3) Dielectric loss as a function of temperature for different content of (a) TiO₂ and (b) ZnO- epoxy composite.

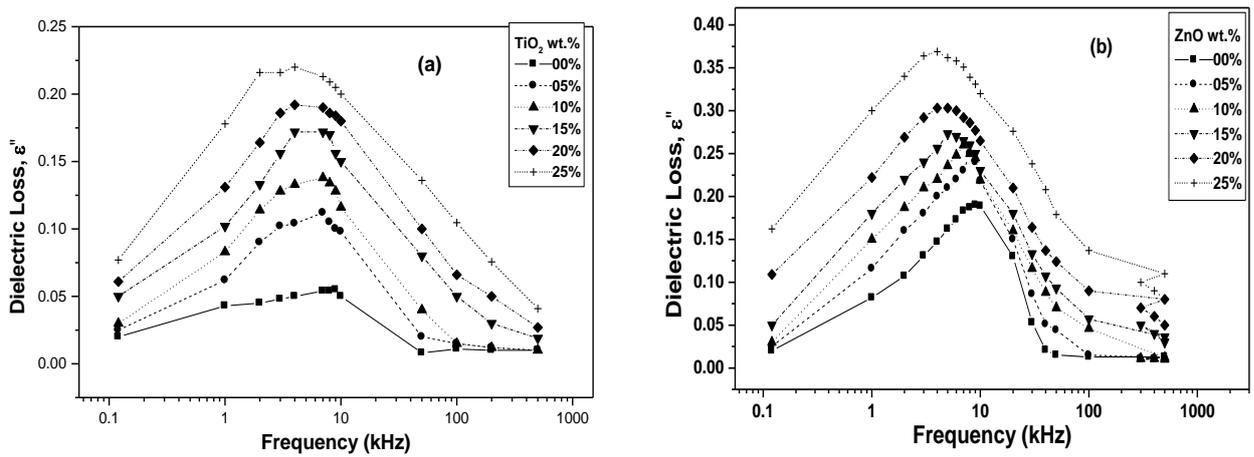


Fig. (5) Dielectric Loss as a function of filler content and frequency for different content of (a) TiO_2 and (b) ZnO- epoxy composite.

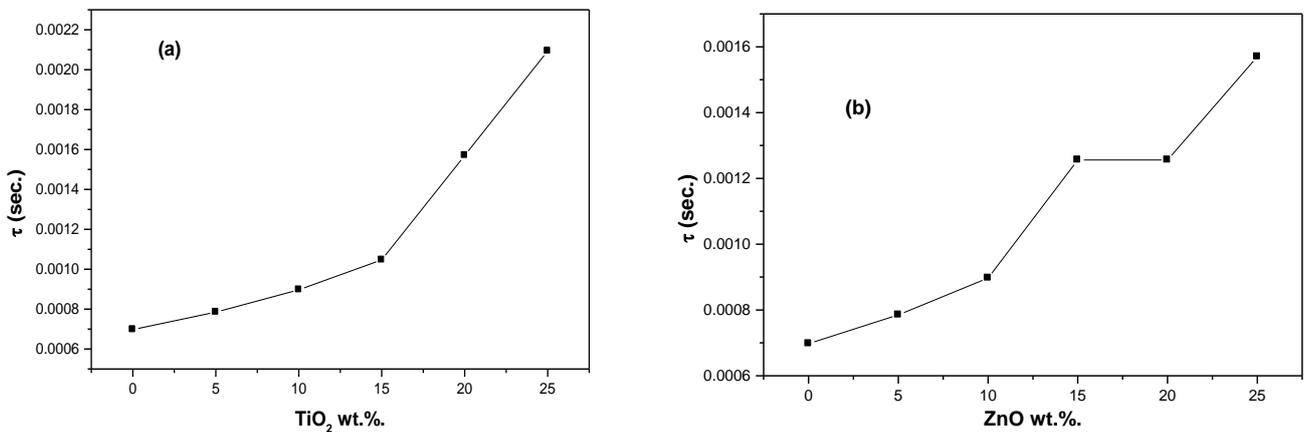


Fig. (6) Relaxation time as a function of filler content for (a) TiO_2 and (b) ZnO- epoxy composite.

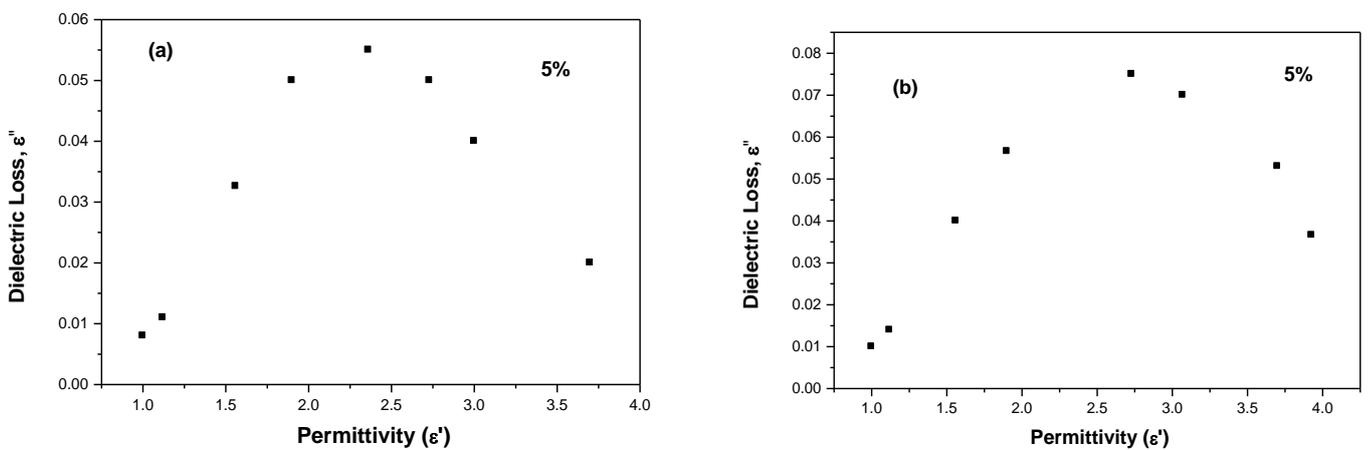


Fig. (7) Cole-Cole diagram for (a) TiO_2 - epoxy composite and (b) ZnO- epoxy composite.

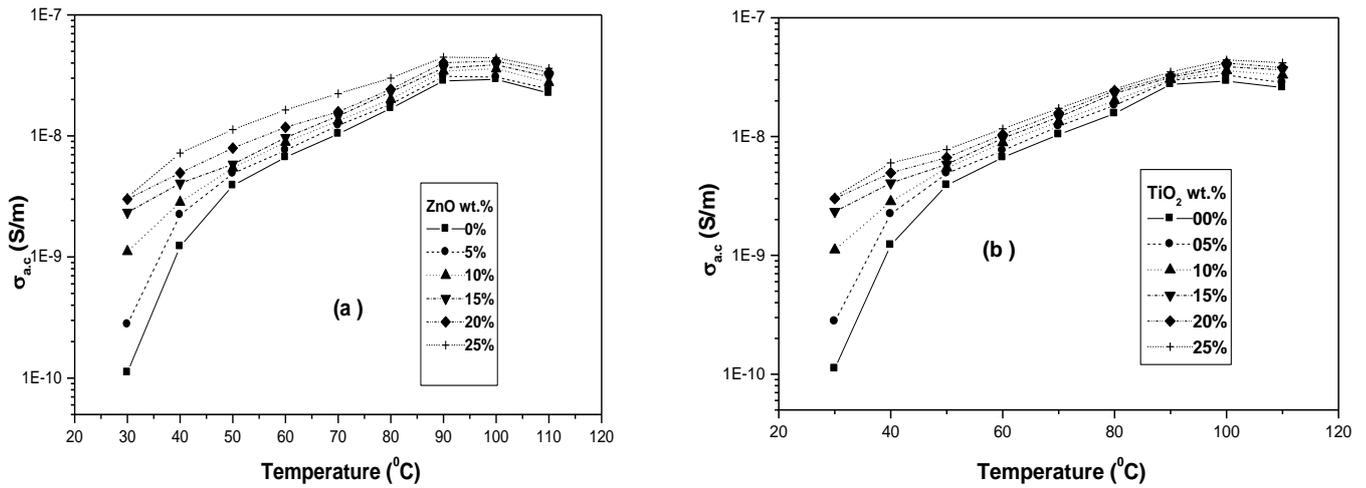


Fig. (8) Ac conductivity as a function of temperature for different content of (a) TiO₂ and (b) ZnO- epoxy composite.

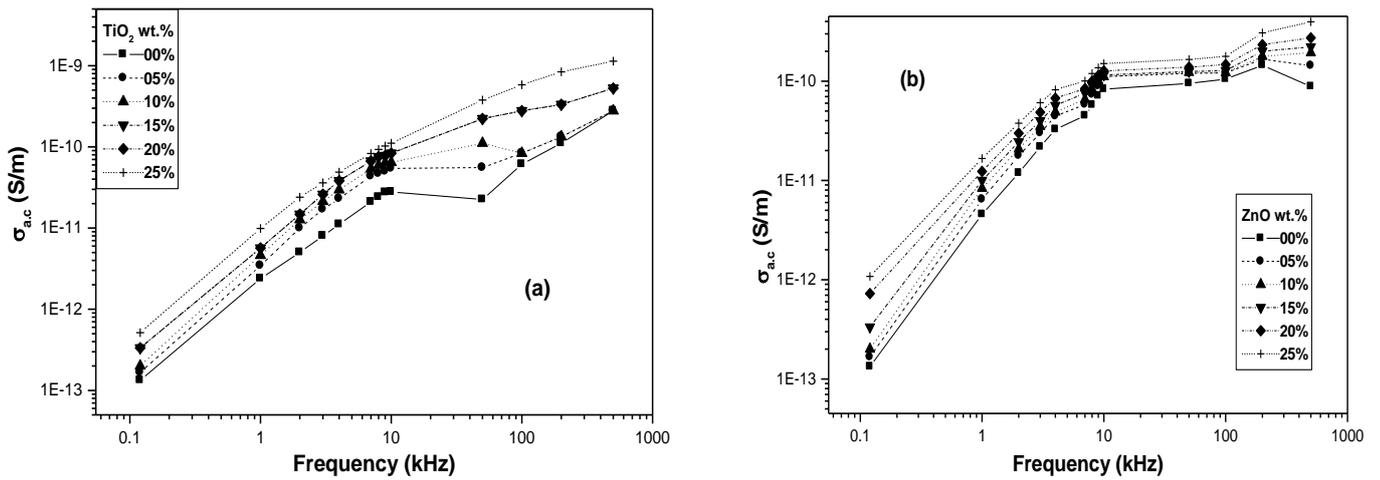


Fig.(9) AC conductivity as a function of frequency for different content of (a) TiO₂ and (b) ZnO- epoxy composite.

References:

- [1] L.A. Ramajo, M.A. Ramirez and P.R. Bueno, *J. Mater. Res.*, 11, 85-88, (2008) .
- [2] D.H. Kuo, C.C Chang and T.Y.Su, *J. Eurp. Ceram. Soc*, 21, 1171-1177, (2001).
- [3] R. Popielarz, C.K. Chiang, R. Zozaki and J. Obrzut, *J. Am. Chem. Soc.*, 34, 5910-5915, (2001).
- [4] G.M. Tsangaris, N. Kouloumbi and S. Kyvelidis, *J. Mater. Chem & Phys.*, 44, 245-250, (1996).
- [5] P. Gonon, T.P. Hong, O. Lesaint, S. Bourdelais and H. Debruyne, *Poly. Test.*, 24, 799-804, (2005).
- [6] L.A. Ramajo, M. Reboledo, D. Santiago and M. Catro, *J. compos. Mater.*, 42 (2008) .
- [7] D.H. Kuo, C.C. Chang and T.Y. Su, *J. Mater. Chem and Phys.*, 85, 201-206, (2004).
- [8] M. S. Joaged and S. Ducharme, *J. curr. Sci.*, 83, (2002) .
- [9] D. Ravinder and K.V. Kumar, *Bull. Mater. Sci.*, 24, 5, (2001).
- [10] H. J. Park, S.M. Hong, S.S. Lee and M. Park, *IEEE Trans. Adv. Pack.*, 31, (2008) .
- [11] Y. Rao, J. Yue and C.P. Wong, *Act. Pass. Elec. Comp.*, 25, 123-129, (2002).
- [12] W.A. Hussain, Ph.D. Thesis, University of Basrah, Basrah, Iraq. (2006).
- [13] V. Singh, A.R. Kulkarni and T.R. Ramamohan, *J. Appl. Poly. Sci.*, 90, 3602-3608, (2003).
- [14] C.H. Kim and J.S. Shin, *Bull. Korean Chem. Soc.*, 23, (2002).
- [15] L. Ramajo, M. Catro and M. Reboledo, *J. Appl. Sci. Manuf.*, 38, 1852-1959, (2007).
- [16] J. G. Hyun, S. Lee and K.W. Paik, *Kor. Adv. Inst. Sci. Tech.*, (2005).
- [17] C.K. Chiang, R. Popielarz and L.P. Sung, *Mat. Res. Soc. Symp. Proc*, 69, (2001).
- [18] S. Sindhu, M.R. Anantharaman, B.P. Thampi, K.A. Malini and P. Kurian, *Bull. mater. Sci* 25, 599 (2002)
- [19] S.A. Saq'an, A.S. Ayesh, A.M. Zihlif, E. Martuscelli and G. Ragosta, *Polym. Test.*, 23, 739-745, (2004).
- [20] G.C. Psarras, E. Manolakaki and G.M. Tsangaris, *Composites part A*, 375 (2002).
- [21] P. Gonon, A. Sylvester, J. Teyseyre and C. prior, *J. Mater. Sci.*, 81, (2001).
- [22] N. Hadik, A. Outzourhit, A. Elmansouri, A. Abouelaoualim, A. Oueriagli, and E. L. Ameziane, "Active and Passive Electronic Components" , 6, (2009).
- [23] D. K. Pradhan, R.N.P. Choundhary, B.K. Samantaray, "Int. J. Electro. Sci.", 3, 597-608, (2008).
- [24] C.C. Cheng, C. M. Lin, S.F. Wang and S.T. Lin, "Matt. Lett.", 61, 757-760, (2007).
- [25] J. P. Lei, Y. Li and K S. Zhao, "Chin. Chem. Lett.", 11, 8, 739-724, (2000).
- [26] S. Singha and M. J. Thomas, "IEEE Trans. Dielect. Elect. Ins.", 15, 1, (2008).
- [27] D. K. Pradhan, R.N.P. Choundhary, B.K. Samantaray, "Int. J. Electro. Sci.", 3, 597-608, (2008).
- [28] G. G. Raju, "Dielectric in Electric Field", Marcel Dekker, Inc, USA, (2003).
- [29] A. A. Hussain and W. A. Hussain "J. Basrah Res. (Sci.)", 36, 13, (2010).
- [30] N. Chand and D. Jain, "Bull. Mater. Sci.", 27, 227-233, (2004).